

An Introduction to Geotextiles in Pavement and Drainage Applications



Guyer Partners
44240 Clubhouse Drive
El Macero, CA 95618
(530)7758-6637
jpguyer@pacbell.net

J. Paul Guyer, P.E., R.A.

Paul Guyer is a registered civil engineer, mechanical engineer, fire protection engineer, and architect with over 35 years experience in the design of buildings and related infrastructure. For an additional 9 years he was a senior advisor to the California Legislature on infrastructure and capital outlay issues. He is a graduate of Stanford University and has held numerous national, state and local positions with the American Society of Civil Engineers and National Society of Professional Engineers.

Introduction to Geotextiles in Pavement & Drainage Applications

Course No: C02-019

Credit: 2 PDH

J. Paul Guyer, P.E., R.A., Fellow ASCE, Fellow AEI



Continuing Education and Development, Inc.
9 Greyridge Farm Court
Stony Point, NY 10980

P: (877) 322-5800

F: (877) 322-4774

info@cedengineering.com

This course is adapted from the *Unified Facilities Criteria* of the United States government, which is in the public domain, has unlimited distribution and is not copyrighted.

CONTENTS

1. GEOTEXTILES IN GENERAL

1.1 Scope

1.2 Geotextile Types and Construction

1.3 Geotextile Durability

1.4 Geotextile Functions and Applications

2. PAVEMENT APPLICATIONS

2.1 Applications

2.2 Paved Surface Rehabilitation

2.3 Reflective Crack Treatment for Pavements

2.4 Separation and Reinforcement

2.5 Design for Separation

2.6 Geotextile Survivability

2.7 Design for Reinforcement

3. DRAINAGE APPLICATIONS

3.1 Water Control

3.2 Granular Drain Performance

3.3 Geotextile Characteristics Influencing Filter Functions

3.4 Piping Resistance

3.5 Permeability

3.6 Other Filter Considerations

3.7 Strength Requirements

3.8 Design and Construction Considerations

1. GEOTEXTILES IN GENERAL

1.1 Scope

This course covers physical properties, functions, design methods, design details and construction procedures for geotextiles as used in pavements and drainage applications. Geotextile functions described include pavements, filtration and drainage. This course does not cover the use of other geosynthetics such as geogrids, geonets, geomembranes, plastic strip drains, composite products and products made from natural cellulose fibers.

1.2 Geotextile Types and Construction

1.2.1 Materials. Geotextiles are made from polypropylene, polyester, polyethylene, polyamide (nylon), polyvinylidene chloride, and fiberglass. Polypropylene and polyester are the most used. Sewing thread for geotextiles is made from Kevlar or any of the above polymers. The physical properties of these materials can be varied by the use of additives in the composition and by changing the processing methods used to form the molten material into filaments. Yarns are formed from fibers which have been bundled and twisted together, a process also referred to as spinning. (This reference is different from the term spinning as used to denote the process of extruding filaments from a molten material.) Yarns may be composed of very long fibers (filaments) or relatively short pieces cut from filaments (staple fibers).

1.2.2 Geotextile Manufacture.

1.2.2.1 In woven construction, the warp yarns, which run parallel with the length of the panel (machine direction), are interlaced with yarns called fill or filling yarns, which run perpendicular to the length of the panel (cross direction as shown in Figure 1-1). Woven construction produces geotextiles with high strengths and moduli in the warp and fill directions and low elongations at rupture. The modulus varies depending on the rate and the direction in which the geotextile is loaded. When woven geotextiles are pulled on a bias, the modulus decreases, although the ultimate breaking strength may


increase. The construction can be varied so that the finished geotextile has equal or different strengths in the warp and fill directions. Woven construction produces geotextiles with a simple pore structure and narrow range of pore sizes or openings between fibers. Woven geotextiles are commonly plain woven, but are sometimes made by twill weave or leno weave (a very open type of weave). Woven geotextiles can be composed of monofilaments or multifilament yarns. Multifilament woven construction produces the highest strength and modulus of all the constructions but are also the highest cost. A monofilament variant is the slit-film or ribbon filament woven geotextile. The fibers are thin and flat and made by cutting sheets of plastic into narrow strips. This type of woven geotextile is relatively inexpensive and is used for separation, i.e., the prevention of intermixing of two materials such as aggregate and fine-grained soil.

1.2.2.2 Manufacturers literature and textbooks should be consulted for greater description of woven and knitted geotextile manufacturing processes which continue to be expanded.

1.2.2.3 Nonwoven geotextiles are formed by a process other than weaving or knitting, and they are generally thicker than woven products. These geotextiles may be made either from continuous filaments or from staple fibers. The fibers are generally oriented randomly within the plane of the geotextile but can be given preferential orientation. In the spun-bonding process, filaments are extruded, and laid directly on a moving belt to form the mat, which is then bonded by one of the processes described below.

- **Needle punching.** Bonding by needle punching involves pushing many barbed needles through one or several layers of a fiber mat normal to the plane of the geotextile. The process causes the fibers to be mechanically entangled. The resulting geotextile has the appearance of a felt mat.
- **Heat bonding.** This is done by incorporating fibers of the same polymer type but having different melting points in the mat, or by using heterofilaments, that is, fibers composed of one type of polymer on the inside and covered or sheathed with a polymer having a lower melting point.
- **Resin bonding.** Resin is introduced into the fiber mat, coating the fibers and bonding the contacts between fibers.

- **Combination bonding.** Sometimes a combination of bonding techniques is used to facilitate manufacturing or obtain desired properties.

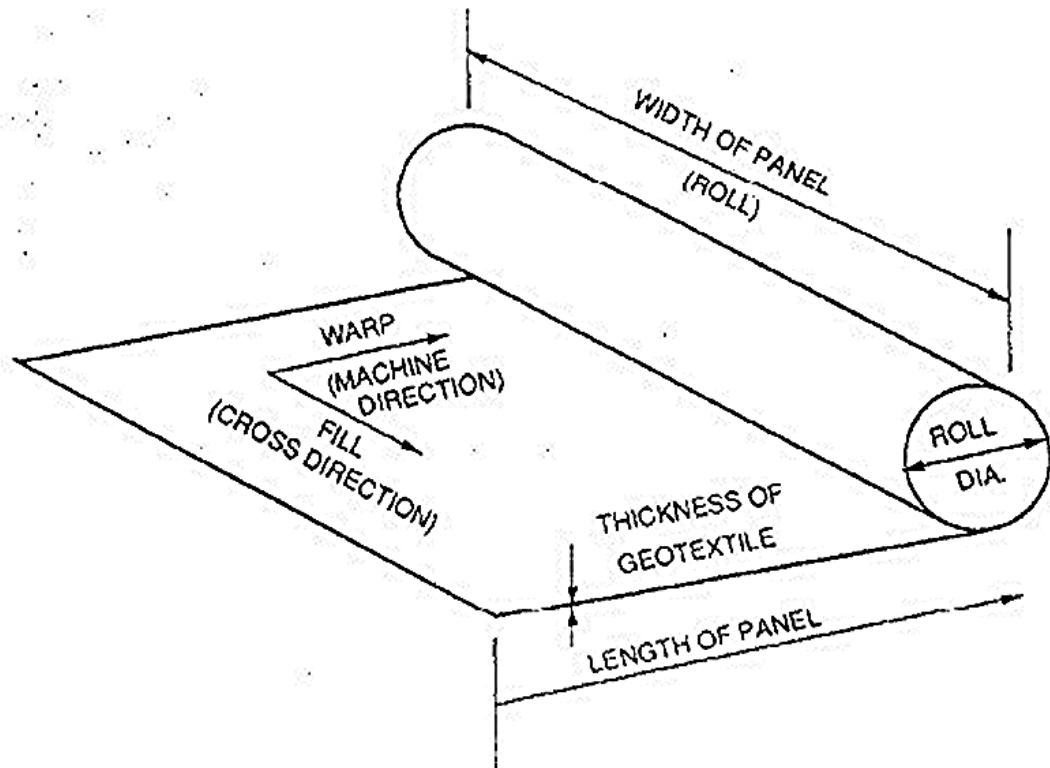

Dimensions and Directions for Woven Geotextiles

Figure 1-1

1.2.2.4 Composite geotextiles are materials which combine two or more of the fabrication techniques. The most common composite geotextile is a nonwoven mat that has been bonded by needle punching to one or both sides of a woven scrim.

1.3 Geotextile Durability

Exposure to sunlight degrades the physical properties of polymers. The rate of degradation is reduced by the addition of carbon black but not eliminated. Hot asphalt can approach the melting point of some polymers. Polymer materials become brittle in very cold temperatures. Chemicals in the groundwater can react with polymers. All

polymers gain water with time if water is present. High pH water can be harsh on polyesters while low pH water can be harsh on polyamides. Where a chemically unusual environment exists, laboratory test data on effects of exposure of the geotextile to this environment should be sought. Experience with geotextiles in place spans only about 30 years. All of these factors should be considered in selecting or specifying acceptable geotextile materials. Where long duration integrity of the material is critical to life safety and where the in-place material cannot easily be periodically inspected or easily replaced if it should become degraded (for example filtration and/or drainage functions within an earth dam), current practice is to use only geologic materials (which are orders of magnitude more resistant to these weathering effects than polyesters).

1.4 Geotextile Functions and Applications.

1.4.1 Functions. Geotextiles perform one or more basic functions: filtration, drainage, separation, erosion control, sediment control, reinforcement, and (when impregnated with asphalt) moisture barrier. In any one application, a geotextile may be performing several of these functions.

1.4.2 Filtration. The use of geotextiles in filter applications is probably the oldest, the most widely known, and the most used function of geotextiles. In this application, the geotextile is placed in contact with and down gradient of soil to be drained. The capacity for flow of water normal to the plane of the geotextile is referred to as permittivity. Water and any particles suspended in the water which are smaller than a given size flow through the geotextile. Those soil particles larger than that size are stopped and prevented from being carried away. The geotextile openings should be sized to prevent soil particle movement. The geotextiles substitute for and serve the same function as the traditional granular filter. Both the granular filter and the geotextile filter must allow water (or gas) to pass without significant buildup of hydrostatic pressure. A geotextile-lined drainage trench along the edge of a road pavement is an example using a geotextile as a filter. Most geotextiles are capable of performing this function. Slit film

geotextiles are not preferred because opening sizes are unpredictable. Long term clogging is a concern when geotextiles are used for filtration.

1.4.3 Drainage. When functioning as a drain, a geotextile acts as a conduit for the movement of liquids or gases in the plane of the geotextile. Examples are geotextiles used as wick drains and blanket drains. The relatively thick nonwoven geotextiles are the products most commonly used. Selection should be based on transmissivity, which is the capacity for in-plane flow. Questions exist as to long term clogging potential of geotextile drains. They are known to be effective in short duration applications.

1.4.4 Erosion Control. In erosion control the geotextile protects soil surfaces from the tractive forces of moving water or wind and rainfall erosion. Geotextiles can be used in ditch linings to protect erodible fine sands or cohesionless silts. The geotextile is placed in the ditch and is secured in place by stakes or is covered with rock or gravel to secure the geotextile, shield it from ultraviolet light, and dissipate the energy of the flowing water. Geotextiles are also used for temporary protection against erosion on newly seeded slopes. After the slope has been seeded, the geotextile is anchored to the slope holding the soil and seed in-place until the seeds germinate and vegetative cover is established. The erosion control function can be thought of as a special case of the combination of the filtration and separation functions.

1.4.5 Sediment Control. A geotextile serves to control sediment when it stops particles suspended in surface fluid flow while allowing the fluid to pass through. After some period of time, particles accumulate against the geotextile, reducing the flow of fluid and increasing the pressure against the geotextile. Examples of this application are silt fences placed to reduce the amount of sediment carried off construction sites and into nearby water courses. The sediment control function is actually a filtration function.

1.4.6 Reinforcement. In the most common reinforcement application, the geotextile interacts with soil through frictional or adhesion forces to resist tensile or shear forces. To provide reinforcement, a geotextile must have sufficient strength and embedment

length to resist the tensile forces generated, and the strength must be developed at sufficiently small strains (i.e. high modulus) to prevent excessive movement of the reinforced structure. To reinforce embankments and retaining structures, a woven geotextile is recommended because it can provide high strength at small strains.

1.4.7 Separation. Separation is the process of preventing two dissimilar materials from mixing. In this function, a geotextile is most often required to prevent the undesirable mixing of fill and natural soils or two different types of fills. A geotextile can be placed between a railroad subgrade and track ballast to prevent contamination and resulting strength loss of the ballast by intrusion of the subgrade soil. In construction of roads over soft soil, a geotextile can be placed over the soft subgrade, and then gravel or crushed stone placed on the geotextile. The geotextile prevents mixing of the two materials.

1.4.8 Moisture Barrier. Both woven and nonwoven geotextiles can serve as moisture barriers when impregnated with bituminous, rubber-bitumen, or polymeric mixtures. Such impregnation reduces both the cross-plane and in-plane flow capacity of the geotextiles to a minimum. This function plays an important role in the use of geotextiles in paving overlay systems. In such systems, the impregnated material seals the existing pavement and reduces the amount of surface water entering the base and subgrade. This prevents a reduction in strength of these components and improves the performance of the pavement system.

2. PAVEMENT APPLICATIONS

2.1 Applications

This discussion covers the use of geotextiles for asphalt concrete (AC) overlays on roads and airfields and the separation and reinforcement of materials in new construction. The functions performed by the geotextile and the design considerations are different for these two applications. In an AC pavement system, the geotextile provides a stress-relieving interlayer between the existing pavement and the overlay that reduces and retards reflective cracks under certain conditions and acts as a moisture barrier to prevent surface water from entering the pavement structure. When a geotextile is used as a separator, it is placed between the soft subgrade and the granular material. It acts as a filter to allow water but not fine material to pass through it, preventing any mixing of the soft soil and granular material under the action of the construction equipment or subsequent traffic.

2.2 Paved Surface Rehabilitation

2.2.1 General. Old and weathered pavements contain transverse and longitudinal cracks that are both temperature and load related. The method most often used to rehabilitate these pavements is to overlay the pavement with AC. This temporarily covers the cracks. After the overlay has been placed, any lateral or vertical movement of the pavement at the cracks due to load or thermal effects causes the cracks from the existing pavement to propagate up through the new AC overlay (called reflective cracking). This movement causes raveling and spalling along the reflective cracks and provides a path for surface water to reach the base and subgrade which decreases the ride quality and accelerates pavement deterioration.

2.2.2 Concept. Under an AC overlay, a geotextile may provide sufficient tensile strength to relieve stresses exerted by movement of the existing pavement. The geotextile acts as a stress-relieving interlayer as the cracks move horizontally or


vertically. A typical pavement structure with a geotextile interlayer is shown in Figure 2-1. Impregnation of the geotextile with a bitumen provides a degree of moisture protection for the underlying layers whether or not reflective cracking occurs.

2.3 Reflective Crack Treatment for Pavements

2.3.1 General. Geotextiles can be used successfully in pavement rehabilitation projects. Conditions that are compatible for the pavement applications of geotextiles are AC pavements that may have transverse and longitudinal cracks but are relatively smooth and structurally sound, and PCC pavements that have minimum slab movement. The geographic location and climate of the project site have an important part in determining whether or not geotextiles can be successfully used in pavement rehabilitation. Geotextiles have been successful in reducing and retarding reflective cracking in mild and dry climates when temperature and moisture changes are less likely to contribute to movement of the underlying pavement; whereas, geotextiles in cold climates have not been as successful. Figure 2-2 gives guidance in using geotextiles to minimize reflective cracking on AC pavements. Geotextiles interlayers are recommended for use in Areas I and II, but are not recommended for use in Area III. Since geotextiles do not seem to increase the performance of thin overlays, minimum overlay thicknesses for Areas I and II are given in Figure 2-2. Even when the climate and thickness requirements are met, there has been no consistent increase in the time it takes for reflective cracking to develop in the overlay indicating that other factors are influencing performance. Other factors affecting performance of geotextile interlayers are construction techniques involving pavement preparation, asphalt sealant application, geotextile installation, and AC overlay as well as the condition of the underlying pavement.


2.3.2 Surface Preparation. Prior to using geotextiles to minimize reflective cracks, the existing pavement should be evaluated to determine pavement distress. The size of the cracks and joints in the existing pavement should be determined. All cracks and joints larger than $\frac{1}{4}$ inch in width should be sealed. Differential slab movement should be

evaluated, since deflections greater than 0.002 inch cause early reflective cracks. Areas of the pavement that are structurally deficient should be repaired prior to geotextile installation. Placement of a leveling course is recommended when the existing pavement is excessively cracked and uneven.

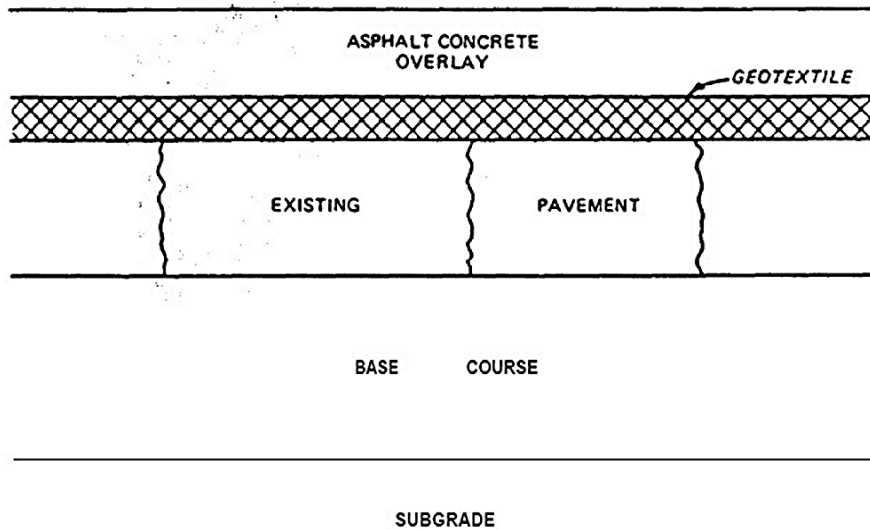

Geotextile in Asphalt Concrete Overlay

Figure 2-1

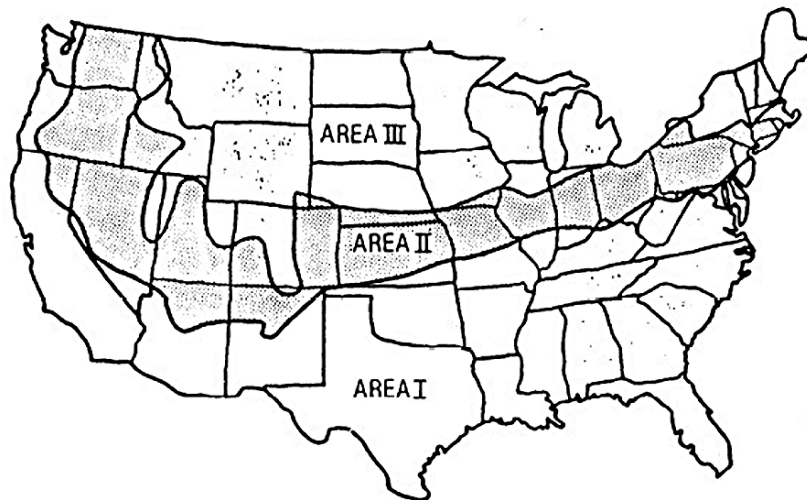

AREA I- INTERLAYERS ARE RECOMMENDED WITH MINIMUM OVERLAY THICKNESS OF 2 IN.

AREA II- INTERLAYERS ARE RECOMMENDED WITH OVERLAY THICKNESS OF 3-4 IN.

AREA III -INTERLAYERS ARE NOT RECOMMENDED.

Guidance for Geotextile Use in Minimizing Reflective Cracking

Figure 2-2

2.3.3 Geotextile Selection.

2.3.3.1 Geotextile interlayers are used in two different capacities-the full-width and strip methods. The full-width method involves sealing cracks and joints and placing a nonwoven material across the entire width of the existing pavement. The material should have the properties shown in Table 2-1. Nonwoven materials provide more flexibility and are recommended for reflective crack treatment of AC pavements.

2.3.3.2 The strip method is primarily used on Portland cement concrete (PCC) pavements and involves preparing the existing cracks and joints, and placing a 12 to 24 inch wide geotextile and sufficient asphalt directly on the cracks and joints. The required physical properties are shown in Table 2-1, however nonwoven geotextiles are not normally used in the strip method. Membrane systems have been developed for strip repairs.

2.3.4 Asphalt Sealant. The asphalt sealant is used to impregnate and seal the geotextile and bond it to both the base pavement and overlay. The grade of asphalt cement specified for hot-mix AC pavements in each geographic location is generally the most acceptable material. Either anionic or cationic emulsion can also be used. Cutback asphalts and emulsions which contain solvents should not be used.

2.3.5 AC Overlay. The thickness of the AC overlay should be determined from the pavement structural requirements. For AC pavements, Area I shown in Figure 2-2 should have a minimum overlay thickness of 2 inches; whereas, Area II should have a minimum overlay thickness of 3 inches. The minimum thickness of an AC overlay for geotextile application on PCC pavements is 4 inches.

2.3.6 Spot Repairs. Rehabilitation of localized distressed areas and utility cuts can be improved with the application of geotextiles. Isolated distressed areas that are excessively cracked can be repaired with geotextiles prior to an AC overlay. A full-width membrane strip application can be used depending on the size of the distressed area. Localized distressed areas of existing AC pavement that are caused by base failure

should be repaired prior to any pavement rehabilitation. Geotextiles are not capable of bridging structurally deficient pavements.

| <i>Property</i> | <i>Requirements</i> | <i>Test Method</i> |
|--|---------------------|----------------------|
| Breaking load, pounds/inch of width | 80 minimum | ASTM D 4632 |
| Elongation-at-break, percent | 50 minimum | ASTM D 4632 |
| Asphalt retention, gallons per square yard | 0.2 minimum | AASHTO M288 |
| Melting point, degrees Fahrenheit | 300 minimum | ASTM D 276 |
| Weight, ounce per square yard | 3-9 | ASTM D 3776 Option B |

Property Requirements of Nonwoven Geotextiles.

Table 2-1

2.4 Separation and Reinforcement

Soft subgrade materials may mix with the granular base or subbase material as a result of loads applied to the base course during construction and/or loads applied to the pavement surface that force the granular material downward into the soft subgrade or as a result of water moving upward into the granular material and carrying the subgrade material with it. A sand blanket or filter layer between the soft subgrade and the granular material can be used in this situation. Also, the subgrade can be stabilized with lime or cement or the thickness of granular material can be increased to reduce the stress on the subgrade. Geotextiles have been used in construction of gravel roads and airfields over soft soils to solve these problems and either increase the life of the pavement or reduce the initial cost. The placement of a permeable geotextile between the soft subgrade and the granular material may provide one or more of the following functions: (1) a filter to allow water but not soil to pass through it, (2) a separator to prevent the mixing of the soft soil and the granular material, and (3) a reinforcement layer to resist the development of rutting. The reinforcement application is primarily for gravel surfaced pavements. The required thicknesses of gravel surfaced roads and airfields have been reduced because of the presence of the geotextile. There is no established criteria for designing gravel surfaced airfields containing a geotextile.

2.5 Design for Separation

When serving as a separator, the geotextile prevents fines from migrating into the base course and/or prevents base course aggregate from penetrating into, the subgrade. The soil retention properties of the geotextile are basically the same as those required for drainage or filtration. Therefore, the retention and permeability criteria required for drainage should be met. In addition, the geotextile should withstand the stresses resulting from the load applied to the pavement. The nature of these stresses depend on the condition of the subgrade, type of construction equipment, and the cover over the subgrade. Since the geotextile serves to prevent aggregate from penetrating the subgrade, it must meet puncture, burst, grab and tear strengths specified in the following paragraphs.

2-6. Geotextile Survivability

Table 2-2 has been developed for the Federal Highway Administration (FHWA) to consider survivability requirements as related to subgrade conditions and construction equipment; whereas, table 2-3 relates survivability to cover material and construction equipment. Table 2-4 gives minimum geotextile grab, puncture, burst, and tear strengths for the survivability required for the conditions indicated in tables 2-2 and 2-3.

2-7. Design for Reinforcement

Use of geotextiles for reinforcement of gravel surfaced roads is generally limited to use over soft cohesive soils (CBR < 4). One procedure for determining the thickness requirements of aggregate above the geotextile was developed by the US Forest Service (Steward, et al. 1977) and is as follows:

2.7.1 Determine In-Situ Soil Strength. Determine the in-situ soil strength using the field California Bearing Ratio (CBR), cone penetrometer, or Vane Shear device. Make several readings and use the lower quartile value.

2.7.2 Convert Soil Strength. Convert the soil strength to an equivalent cohesion (C) value using the correlation shown in Figure 2-3. The shear strength is equal to the C value.

| Site Soil CBR at Installation | <1 | | 1-2 | | >2 | |
|---|-----|-----|-----|-----|-----|-----|
| Equipment Ground Contact Pressure (psi) | >50 | <50 | >50 | <50 | >50 | <50 |
| Cover Thickness (in.) (Compacted) | | | | | | |
| 4,2,3 | NR | NR | H | M | M | M |
| 6 | NR | NR | H | H | M | M |
| 12 | NR | H | M | M | M | M |
| 18 | H | M | M | M | M | M |

H = High, M = Medium, NR = Not recommended.

¹Maximum aggregate size not to exceed one half the compacted cover thickness.

²For low volume unpaved road (ADT 200 vehicles).

³The four inch minimum cover is limited to existing road bases and not intended for use in new construction.

Construction Survivability Ratings (FHWA 1989)

Table 2-2

| Variable | Severity Category | | |
|-------------------------|----------------------------|---|---|
| | LOW | Moderate | High to Very High |
| Equipment | Light weight dozer (8 psi) | Medium weight dozer; light wheeled equipment (8-40 psi) | Heavy weight dozer; loaded dump truck (>40 psi) |
| Subgrade Condition | Cleared | Partially cleared | Not cleared |
| Subgrade Strength (CBR) | <0.5 | 1-2 | >3 |
| Aggregate | Rounded sandy gravel | Coarse angular gravel | Cobbles, blasted rock |
| Lift Thickness (in.) | 18 | 12 | 6 |

Relationship of Construction Elements to Severity of Loading Imposed on Geotextile in Roadway Construction

Table 2-3

| Required Degree of Geotextile Survivability | Grab Strength' lb | Puncture Strength' lb | Burst Strength' psi | Trap Tear' lb |
|---|-------------------|-----------------------|---------------------|---------------|
| Very high | 270 | 110 | 430 | 75 |
| High | 180 | 75 | 290 | 50 |
| Moderate | 130 | 40 | 210 | 40 |
| Low | 90 | 30 | 145 | 30 |

Note: All values represent minimum average roll values (i.e., any roll in a lot should meet or exceed the minimum values in this table). These values are normally 20 percent lower than manufacturers reported typical values.

*ASTM D 4632.


*ASTM D 4833.

*ASTM D 3786.

*ASTM D 4533, either principal direction.

Minimum Geotextile Strength Properties for Survivability

Table 2-4

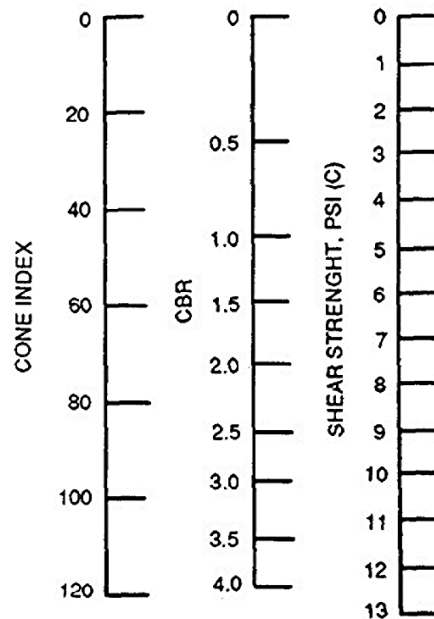

Relationship Between Shear Strength, CBR, and Cone Index

Figure 2-3

2.7.3 Select Design Loading. Select the desired design loading, normally the maximum axle loads.

2.7.4 Determine Required Thickness of Aggregate. Determine the required thickness of aggregate above the geotextile using Figures 2-4, 2-5, and 2-6. These figures relate the depth of aggregate above the geotextile to the cohesion of the soil (C) and to a bearing capacity factor (NC). The product of C and NC is the bearing capacity for a rapidly loaded soil without permitting drainage. The significance of the value used for NC as it relates to the design thickness using Figures 2-4, 2-5, and 2-6 is as follows:

2.7.4.1 For thickness design without using geotextile.

- A value of 2.8 for NC would result in a thickness design that would perform with very little rutting (less than 2 inches) at traffic volumes greater than 1,000 equivalent 18-kip axle loadings.
- A value of 3.3 for NC would result in a thickness design that would rut 4 inches or more under a small amount of traffic (probably less than 100 equivalent 18-kip axle loadings).

2.7.4.2 For thickness design using geotextile.

- A value of 5.0 for NC would result in a thickness design that would perform with very little rutting (less than 2 inches) at traffic volumes greater than 1,000 equivalent 18-kip axle loadings.
- A value of 6.0 for NC would result in a thickness design that would rut 4 inches or more under a small amount of traffic (probably less than 100 equivalent 18-kip axle loadings).

2.7.5 Geotextile reinforced gravel road design example. Design a geotextile reinforced gravel road for a 24,000-pound-tandem-wheel load on a soil having a CBR of 1. The road will have to support several thousand truck passes and very little rutting will be allowed.

2.7.5.1 Determine the required aggregate thickness with geotextile reinforcement.


- From figure 2-3 a 1 CBR is equal to a C value of 4.20.
- Choose a value of 5 for NC since very little rutting will be allowed.

- Calculate CNC as: $CNC = 4.20(5) = 21$.
- Enter figure 2-6 with CNC of 21 to obtain a value of 14 inches as the required aggregate thickness above the geotextile.
- Select geotextile requirements based on
- survivability requirements in tables 2-2 and 2-3.

2.7.5.2 Determine the required aggregate thickness when a geotextile is not used.


- Use a value of 2.8 for NC since a geotextile is not used and only a small amount of rutting will be allowed.
- Calculate CNC as: $CNC = 4.20(2.8) = 11.8$.
- Enter figure 2-6 with CNC of 11.8 to obtain a value of 22 inches as the required aggregate thickness above the subgrade without the geotextile.

2.7.5.3 Compare cost and benefits of the alternatives. Even with nearby economical gravel sources, the use of a geotextile usually is the more economical alternative for constructing low volume roads and airfields over soft cohesive soils. Additionally, it results in a faster time to completion once the geotextiles are delivered on site.

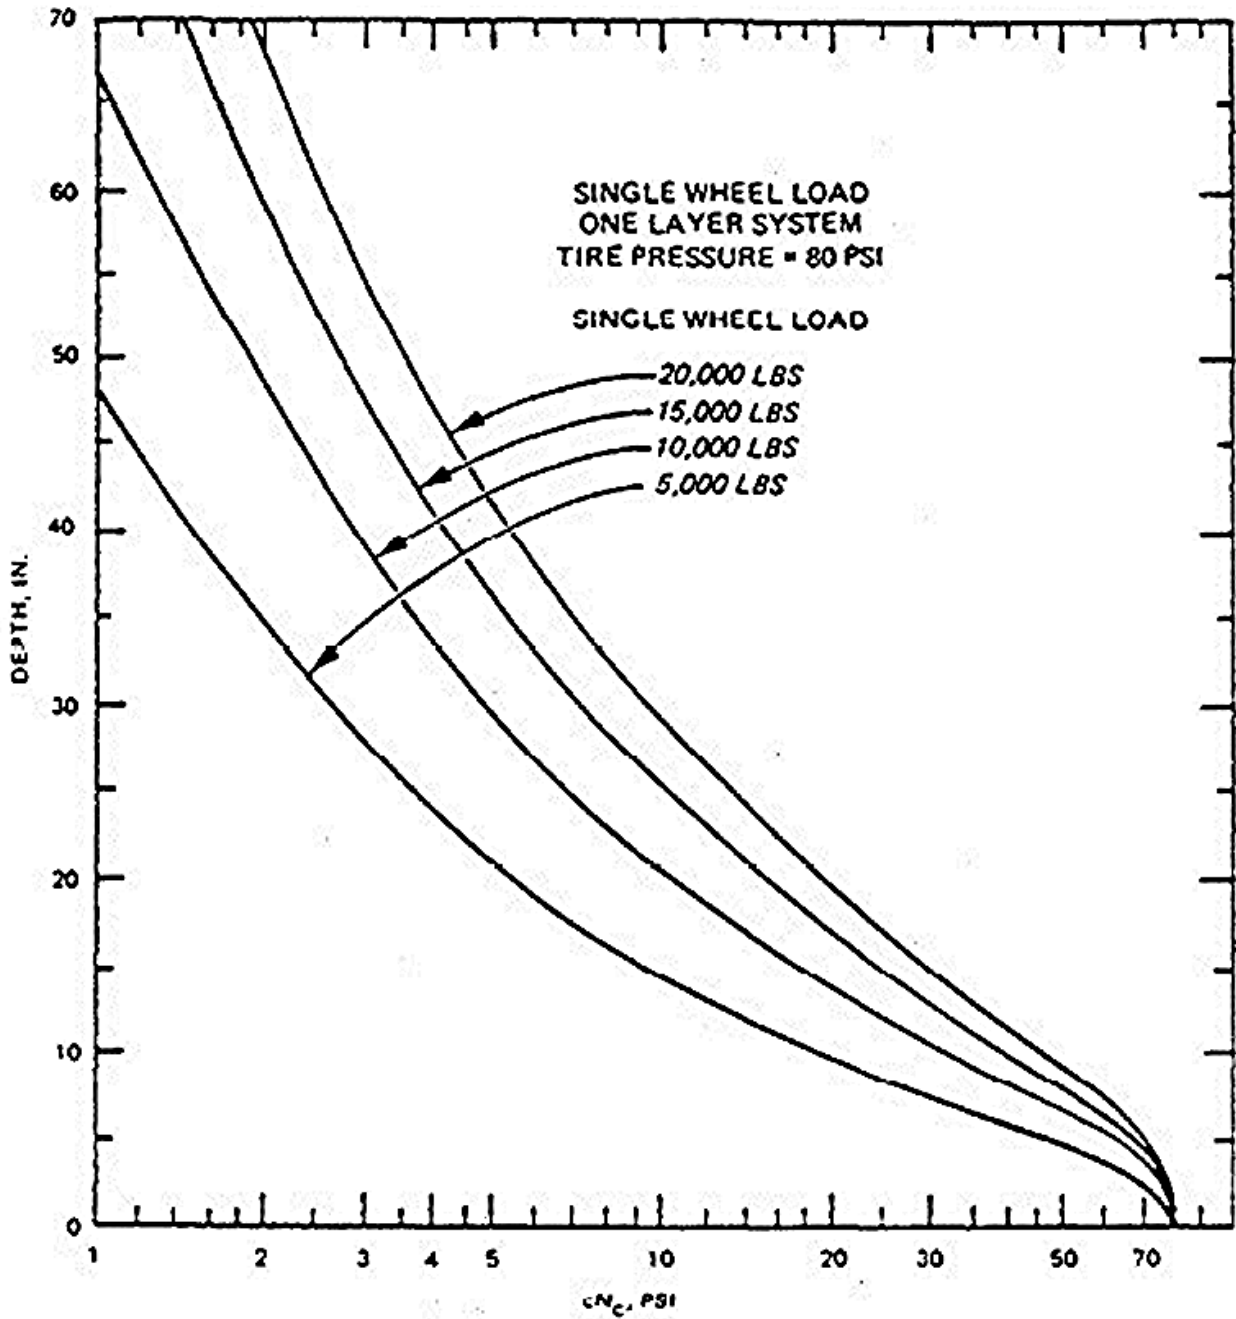


Thickness Design Curve for Single- Wheel Load on Gravel-Surfaced Roads

Figure 2-4

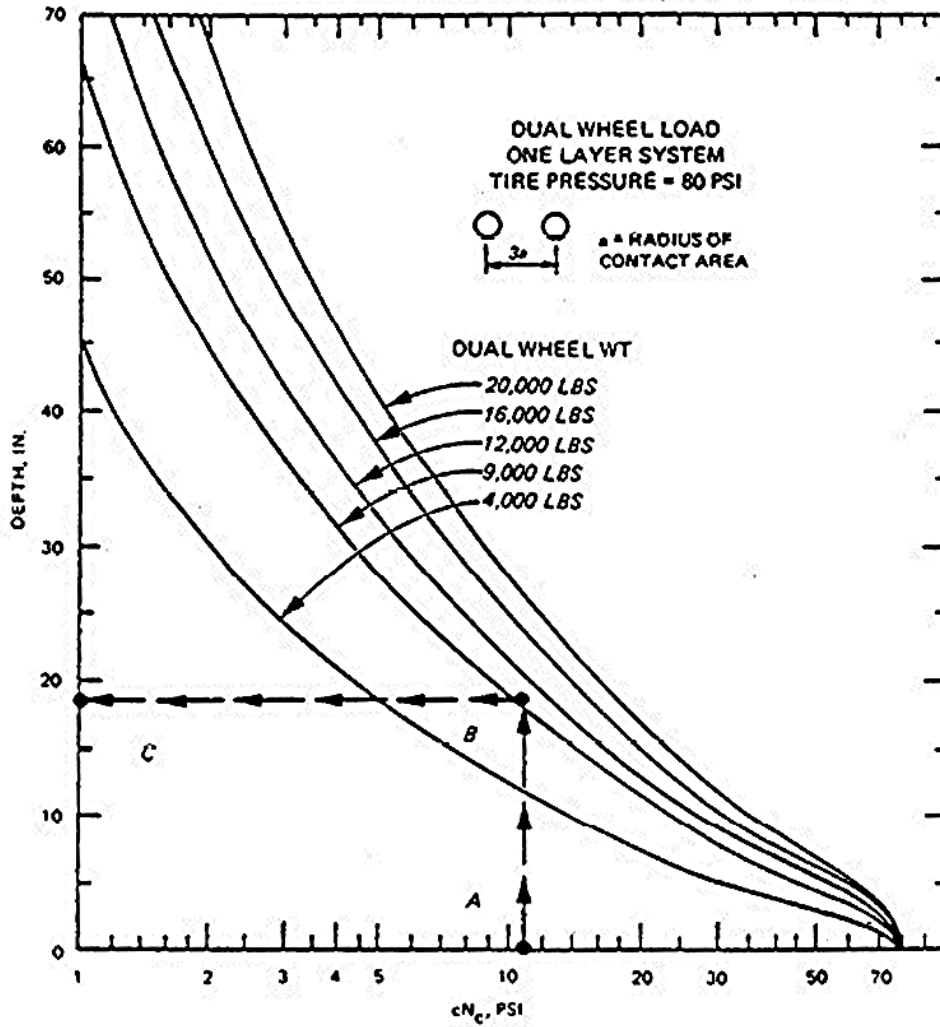

Thickness Design Curve for Dual- Wheel Load on Gravel-Surfaced Roads

Table 2-5

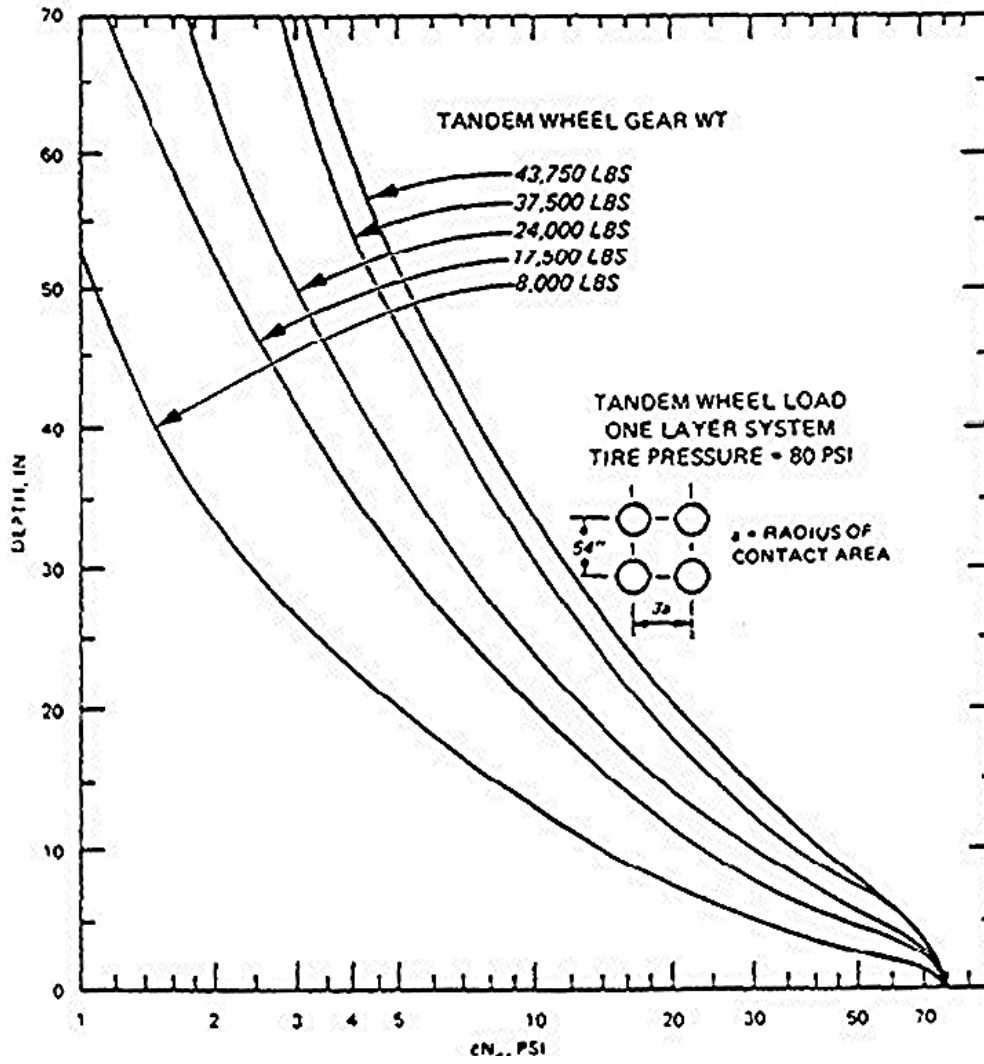

Thickness Design Curve for Tandem- Wheel Load on Gravel-Surfaced Roads

Table 2-6

3. DRAINAGE APPLICATIONS

3.1 Water Control

Control of water is critical to the performance of buildings, pavements, embankments, retaining walls, and other structures. Drains are used to relieve hydrostatic pressure against underground and retaining walls, slabs, and underground tanks and to prevent loss of soil strength and stability in slopes, embankments, and beneath pavements. A properly functioning drain must retain the surrounding soil while readily accepting water from the soil and removing it from the area. These general requirements apply to granular and geotextile filters. While granular drains have a long performance history, geotextile use in drains is relatively recent and performance data are limited to approximately 25 years. Where not exposed to sunlight or abrasive contact with rocks moving in response to moving surface loads or wave action, long-term performance of properly selected geotextiles has been good. Since long-term experience is limited, geotextiles should not be used as a substitute for granular filters within or on the upstream face of earth dams or within any inaccessible portion of the dam embankment. Geotextiles have been used in toe drains of embankments where they are easily accessible if maintenance is required and where malfunction can be detected. Caution is advised in using geotextiles to wrap permanent piezometers and relief wells where they form part of the safety system of a water retaining structure. Geotextiles have been used to prevent infiltration of fine-grained materials into piezometer screens but long-term performance has not been measured.

3.2 Granular Drain Performance

To assure proper performance in granular drains, the designer requires drain materials to meet grain-size requirements based on grain size of the surrounding soil. The two principal granular filter criteria, piping and permeability have been developed empirically through project experience and laboratory testing.

3.3 Geotextile Characteristics Influencing Filter Functions

The primary geotextile characteristics influencing filter functions are opening size (as related to soil retention), flow capacity, and clogging potential. These properties are indirectly measured by the apparent opening size (AOS) (ASTM D 4751), permittivity (ASTM D 4491), and gradient ratio test (ASTM D 5101). The geotextile must also have the strength and durability to survive construction and long-term conditions for the design life of the drain. Additionally, construction methods have a critical influence on geotextile drain performance.

3.4 Piping Resistance

3.4.1 Basic Criteria. Piping resistance is the ability of a geotextile to retain solid particles and is related to the sizes and complexity of the openings or pores in the geotextile. For both woven and nonwoven geotextiles, the critical parameter is the AOS. Table 3-1 gives the relation of AOS to the gradation of the soil passing the number 200 sieve for use in selecting geotextiles.

3.4.2 Percent Open Area Determination Procedure for Woven Geotextiles.

3.4.2.1 Installation of geotextile. A small section of the geotextile to be tested should be installed in a standard 2 by 2 inch slide cover, so that it can be put into a slide projector and projected onto a screen. Any method to hold the geotextile section and maintain it perpendicular to the projected light can be used.

3.4.2.2 Slide projector. The slide projector should be placed level to eliminate any distortion of the geotextile openings. After placing the slide in the projector and focusing on a sheet of paper approximately 8 to 10 feet away, the opening outlines can be traced.

| Protected Soil (Percent Passing No. 200 Sieve) | Piping ¹ | Permeability | |
|--|--|------------------------|-----------------------|
| | | Woven | Nonwoven ² |
| Less than 5% | AOS (mm) < 0.6 (mm) (Greater than #30 US Standard Sieve) | POA ³ > 10% | $k_G > 5k_S$ |
| 5 to 50% | AOS (mm) < 0.6 (mm) (Greater than #30 US Standard Sieve) | POA > 4% | $k_G > 5k_S$ |
| 50 to 85% | AOS (mm) < 0.297 (mm) (Greater than #50 US Standard Sieve) | POA > 4% | $k_G > 5k_S$ |
| Greater than 85% | AOS (mm) < 0.297 (mm) (Greater than #50 US Standard Sieve) | | $k_G > 5k_S$ |

¹ When the protected soil contains appreciable quantities of material retained on the No. 4 sieve use only the soil passing the No. 4 sieve in selecting the AOS of the geotextile.

² k_G is the permeability of the nonwoven geotextile and k_S is the permeability of the protected soil.

³ POA = Percent Open Area.

Geotextile Filter Design Criteria

Table 3-1

3.4.2.3 Representative area. Draw a rectangle of about 0.5 to 1 square foot area on the “projection screen” sheet of paper to obtain a representative area to test; then trace the outline of all openings inside the designated rectangle.

3.4.2.4 Finding the area. After removing the sheet, find the area of the rectangle, using a planimeter. If necessary, the given area may be divided to accommodate the planimeter.

3.4.2.5 Total area of openings. Find the total area of openings inside rectangle, measuring the area of each with a planimeter.

3.4.2.6 Compute percent. Compute POA by the equation:

$$\text{POA} = \frac{\text{Total Area Occupied by Openings}}{\text{Total Area of Test Rectangle}} \times 100$$

3.4.3 Flow Reversals. Piping criteria are based on granular drain criteria for preventing drain material from entering openings in drain pipes. If flow through the geotextile drain installation will be reversing and/or under high gradients (especially if reversals are very quick and involve large changes in head), tests, modeling prototype conditions, should be performed to determine geotextile requirements.

3.4.4 Clogging. There is limited evidence (Giroud 1982) that degree of uniformity and density of granular soils (in addition to the D size) influence the ability of geotextiles to retain the drained soil. For very uniform soils (uniformity coefficient 2 to 4), the maximum AOS may not be as critical as for more well graded soils (uniformity coefficient greater than 5). A gradient ratio test with observation of material passing the geotextile may be necessary to determine the adequacy of the material. In normal soil-geotextile filter systems, detrimental clogging only occurs when there is migration of fine soil particles through the soil matrix to the geotextile surface or into the geotextile. For most natural soils, minimal internal migration will take place. However, internal migration may take place under sufficient gradient if one of the following conditions exists:

3.4.4.1 The soil is very widely graded, having a coefficient of uniformity C_u greater than 20.

3.4.4.2 The soil is gap graded. (Soils lacking a range of grain sizes within their maximum and minimum grain sizes are called “gap graded” or “skip graded” soils.) Should these conditions exist in combination with risk of extremely high repair costs if failure of the filtration system occurs the gradient ratio test may be required.

3.4.5 Clogging Resistance. Clogging is the reduction in permeability or permittivity of a geotextile due to blocking of the pores by either soil particles or biological or chemical deposits. Some clogging takes place with all geotextiles in contact with soil. Therefore, permeability test results can only be used as a guide for geotextile suitability. For woven geotextiles, if the POA is sufficiently large, the geotextiles will be resistant to clogging. The POA has proved to be a useful measure of clogging resistance for woven textiles but is limited to woven geotextiles having distinct, easily measured openings. For geotextiles which cannot be evaluated by POA, soil- geotextile permeameters have been developed for measuring soil-geotextile permeability and clogging. As a measure of the degree to which the presence of geotextile affects the permeability of the soil-geotextile system, the gradient ratio test can be used (ASTM D 5101). The gradient ratio is defined as the ratio of the hydraulic gradient across the geotextile and the 1 inch of soil immediately above the geotextile to the hydraulic gradient between 1 and 3 inches above the geotextile.

3.5 Permeability

3.5.1 Transverse Permeability. After installation, geotextiles used in filtration and drainage applications must have a flow capacity adequate to prevent significant clogging by the soil being drained. This flow capacity must be maintained for the range of flow conditions for that particular installation. For soils, the indicator of flow capacity is the coefficient of permeability as expressed in Darcy's Law. The proper application of Darcy's Law requires that geotextile thickness be considered. Since the ease of flow through a geotextile regardless of its thickness is the property of primary interest, Darcy's Law can be modified to define the term permittivity, Y , with units of sec., as follows:

$$\Psi = \frac{k}{L_f} = \frac{q}{(\Delta h)A}$$

(Eq. 3-1)

where

k = Darcy coefficient of permeability, L/T

L_f = length of flow path (geotextile thickness) over which
 Δh occurs, L

q = hydraulic discharge rate, L³/T

Δh = hydraulic head loss through the geotextile, L

A = total cross-sectional area available to flow, L²

L = units of length

T = units of time

The limitation of directly measuring the permeability and permittivity of geotextiles is that Darcy's Law applies only as long as laminar flow exists. This is very difficult to achieve for geotextiles since the hydraulic heads required to assure laminar flow are so small that they are difficult to accurately measure. Despite the fact that Darcy's equation does not apply for most measurements of permeability, the values obtained are considered useful as a relative measure of the permeabilities and permittivities of various geotextiles. Values of permeability reported in the literature, or obtained from testing laboratories, should not be used without first establishing the actual test conditions used to determine the permeability value. ASTM Method D 4491 should be used for establishing the permeability and permittivity of geotextiles. The permeability of some geotextiles decreases significantly when compressed by surrounding soil or rock. ASTM D 5493 can be used for measuring the permeabilities of geotextiles under load.

3.5.2 In-plane Permeability. Thick nonwoven geotextiles and special products as prefabricated drainage panels and strip drains have substantial fluid flow capacity in their plane. Flow capacity in a plane of a geotextile is best expressed independently of the material's thickness since the thickness of various materials may differ considerably, while the ability to transmit fluid under a given head and confining pressure is the property of interest. The property of in-plane flow capacity of a geotextile is termed "transmissivity," q , and is expressed as:

$$\Theta = k_p t = \frac{q l}{\Theta h w} \quad (\text{eq 3-2})$$

where

k_p = in-plane coefficient of permeability (hydraulic conductivity), L/T

t = thickness of geotextile, L (ASTM D 5199)

q = hydraulic discharge rate, L³/T

l = length of geotextile through which liquid is flowing, L

Δh = hydraulic head loss, L

w = width of geotextile, L

L = units of length, length between geotextile grips

T = units of time

Certain testing conditions must be considered if meaningful values of transmissivity are to be acquired. These conditions include the hydraulic gradients used, the normal pressure applied to the product being tested, the potential for reduction of transmissivity over time due to creep of the drainage material, and the possibility that intermittent flow will result in only partial saturation of the drainage material and reduced flow capacity. ASTM D 4716 may be used for evaluating the transmissivity of drainage materials.

3.5.3 Limiting Criteria. Permeability criteria for nonwoven geotextiles require that the permeability of the geotextile be at least five times the permeability of the surrounding soil. Permeability criteria for woven geotextiles are in terms of the POA. When the protected soil has less than 0.5 percent passing the No. 200 sieve, the POA should be equal to or greater than 10 percent. When the protected soil has more than 5 percent but less than 85 percent passing the No. 200 sieve, the POA should be equal to or greater than 4 percent.

3.6 Other Filter Considerations

3.6.1 To prevent clogging or blinding of the geotextile, intimate contact between the soil and geotextile should be assured during construction. Voids between the soil and geotextile can expose the geotextile to a slurry or muddy water mixture during seepage. This condition promotes erosion of soil behind the geotextile and clogging of the geotextile.

3.6.2 Very fine-grained non-cohesive soils, such as rock flour, present a special problem, and design of drain installations in this type of soil should be based on tests with expected hydraulic conditions using the soil and candidate geotextiles.

3.6.3 As a general rule slit-film geotextiles are unacceptable for drainage applications. They may meet AOS criteria but generally have a very low POA or permeability. The wide filament in many slit films is prone to move relative to the cross filaments during handling and thus change AOS and POA.

3.6.4 The designer must consider that in certain areas an ochre formation may occur on the geotextile. Ochre is an iron deposit usually a red or tan gelatinous mass associated with bacterial slimes. It can, under certain conditions, form on and in subsurface drains. The designer may be able to determine the potential for ochre formation by reviewing local experience with highway, agricultural, embankment, or other drains with local or state agencies. If there is reasonable expectation for ochre formation, use of geotextiles is discouraged since geotextiles may be more prone to clog. Once ochre clogging occurs, removal from geotextiles is generally very difficult to impossible, since chemicals or acids used for ochre removal can damage geotextiles, and high pressure jetting through the perforated pipe is relatively ineffective on clogged geotextiles.

3.7 Strength Requirements

Unless geotextiles used in drainage applications have secondary functions (separation, reinforcement, etc.) requiring high strength, the requirements shown in Table 3-2 will provide adequate strength.

| Strength Type | Test Method | Class A ¹ | Class B ² |
|----------------|-------------|----------------------|----------------------|
| Grab Tensile | ASTM D 4632 | 180 | 80 |
| Seam | ASTM D 4632 | 160 | 70 |
| Puncture | ASTM D 4833 | 80 | 25 |
| Burst | ASTM D 3786 | 290 | 130 |
| Trapezoid Tear | ASTM D 4533 | 50 | 25 |

¹ Class A Drainage applications are for geotextile installation where applied stresses are more severe than Class B applications; i.e., very coarse shape angular aggregate is used, compaction is greater than 95 percent of ASTM D 1557 of maximum density or depth of trench is greater than 10 feet.

² Class B Drainage applications are for geotextile installations where applied stresses are less severe than Class A applications; i.e., smooth graded surfaces having no sharp angular projections, and no sharp angular aggregate, compaction is less than or equal to 95 percent of ASTM D 1557 maximum density.

Geotextile Strength Requirements for Drains

Table 3-2

3.8 Design and Construction Considerations

3.8.1 Installation Factors. In addition to the requirement for continuous, intimate geotextile contact with the soil, several other installation factors strongly influence geotextile drain performance. These include:

3.8.1.1 How the geotextile is held in place during construction.

3.8.1.2 Method of joining consecutive geotextile elements.

3.8.1.3 Preventing geotextile contamination.

3.8.1.4 Preventing geotextile deterioration from exposure to sunlight. Geotextile should retain 70 percent of its strength after 150 hours of exposure to ultraviolet sunlight (ASTM D 4355).

3.8.2 Placement. Pinning the geotextile with long nail-like pins placed through the geotextile into the soil has been a common method of securing the geotextile until the

other components of the drain have been placed; however, in some applications, this method has created problems. Placement of aggregate on the pinned geotextile normally puts the geotextile into tension which increases potential for puncture and reduces contact of the geotextile with soil, particularly when placing the geotextile against vertical and/or irregular soil surfaces. It is much better to keep the geotextile loose but relatively unwrinkled during aggregate placement. This can be done by using small amounts of aggregate to hold the geotextile in place or using loose pinning and re-pinning as necessary to keep the geotextile loose. This method of placement will typically require 10 to 15 percent more geotextile than predicted by measurement of the drain's planer surfaces.

3.8.3 Joints.


3.8.3.1 Secure lapping or joining of consecutive pieces of geotextile prevents movement of soil into the drain. A variety of methods such as sewing, heat bonding, and overlapping are acceptable joints. Normally, where the geotextile joint will not be stressed after installation, a minimum 12-inch overlap is required with the overlapping inspected to ensure complete geotextile-to-geotextile contact. When movement of the geotextile sections is possible after placement, appropriate overlap distances or more secure joining methods should be specified. Field joints are much more difficult to control than those made at the factory or fabrication site and every effort should be made to minimize field joining.

3.8.3.2 Strength requirements for seams may vary from just enough to hold the geotextile sections together for installation to that required for the geotextile. Additional guidance for seams is contained in AASHTO M 288. Seam strength is determined using ASTM 4632.

3.8.4 Trench Drains.


3.8.4.1 Variations of the basic trench drain are the most common geotextile drain application. Typically, the geotextile lines the trench allowing use of a very permeable backfill which quickly removes water entering the drain. Trench drains intercept surface infiltration in pavements and seepage in slopes and embankments as well as lowering ground-water levels beneath pavements and other structures. The normal construction sequence is shown in Figure 3-1. In addition to techniques shown in Figure 3-1, if high compactive efforts are required (e.g., 95 percent of ASTM D 1557 maximum density), the puncture strength requirements should be doubled. Granular backfill does not have to meet piping criteria but should be highly permeable, large enough to prevent movement into the pipe, and meet durability and structural requirements of the project. This allows the designer to be much less stringent on backfill requirements than would be necessary for a totally granular trench drain. Some compaction of the backfill should always be applied.

3.8.4.2 Wrapping of the perforated drain pipe with a geotextile when finer grained filter backfill is used is a less common practice. Normally not used in engineering applications, this method is less efficient than lining the trench with a geotextile because the reduced area of high permeability material concentrates flow and lowers the drain efficiency. Wrapping of the pipe may be useful when finer grained filter materials are best suited because of availability and/or grain size requirements. In this case, the geotextile functions as a cover for the pipe perforations preventing backfill infiltration. If the geotextile can be separated a small distance from the pipe surface, the flow through the geotextile into the pipe openings will be much more efficient. Use of plastic corrugated, perforated pipe with openings in the depressed portion of the corrugation is an easy way of doing this.

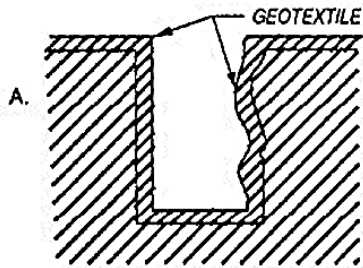


A.

TRENCH EXCAVATED AND GEOTEXTILE PLACED TO INSURE INTIMATE CONTACT WITH SOIL SURFACES AND THAT PROPER OVERLAP WILL BE AVAILABLE AFTER BACK-FILLING

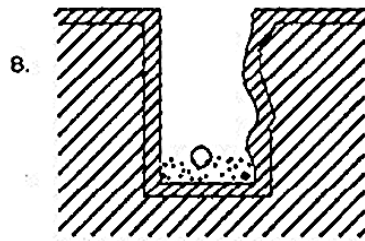


B.

BEDDING (USUALLY 6-INCH MINIMUM) AND COLLECTOR PIPE PLACED (IF PIPE IS REQUIRED)

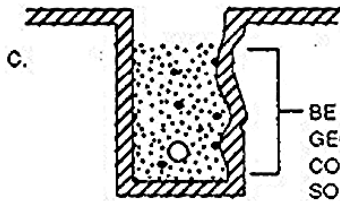

C.

REMAINDER OF BACKFILL PLACED AND COMPACTED AS REQUIRED TO PRODUCE COMPATIBLE STRENGTH AND CONSOLIDATION WITH SURROUNDING SOIL AND STRUCTURES

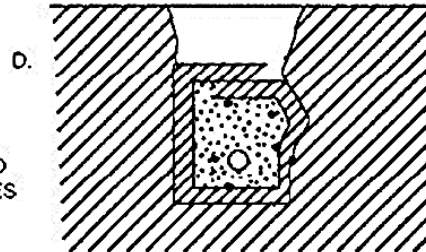

D.

GEOTEXTILE SECURELY OVERLAPPED (USUALLY 12-INCH MINIMUM) ABOVE BACKFILL SO SOIL INFILTRATION IS PREVENTED. COVER MATERIAL PLACED AND COMPACTED

Trench Drain Construction

Figure 3-1